

Nutation: separating the spin from its magnetic moment

Anulekha De^{1,*}, Julius Schlegel^{2,†}, Akira Lentfert¹, Laura Scheuer¹, Benjamin Stadtmüller¹, Philipp Pirro¹,
Georg von Freymann^{1,3}, Ulrich Nowak², and Martin Aeschlimann¹

¹Fachbereich Physik and Landesforschungszentrum OPTIMAS, Rheinland-Pfälzische Technische Universität
Kaiserslautern-Landau, 67663 Kaiserslautern, Germany

²Fachbereich Physik, Universität Konstanz, 78457 Konstanz, Germany

³Fraunhofer Institute for Industrial Mathematics, ITWM 67663 Kaiserslautern, Germany

*Corresponding author: ade@rptu.de

†Corresponding author: julius.schlegel@uni-konstanz.de

For nearly 90 years, precession and relaxation processes have been thought to dominate magnetization dynamics. Only recently has it been considered that, on short time scales, an inertia-driven magnetization dynamics should become relevant, leading to additional nutation of the magnetization vector. Here, we trigger magnetic nutation via a sudden excitation of a thin Ni₈₀Fe₂₀ film with an ultrashort optical pulse, that leads to an abrupt tilting of the effective field acting on the magnetic moments, separating the dynamics of the magnetization from that of its angular momentum. We investigate the resulting magnetization dynamics in the inertial regime experimentally by the time-resolved magneto optical Kerr effect. We find a characteristic oscillation in the Kerr signal in the range of ~ 0.1 THz superimposed on the precessional oscillations with GHz frequencies. By comparison with atomistic spin dynamics simulations, we demonstrate that this observation cannot be explained by the well-known Landau-Lifshitz-Gilbert equation of motion but can be attributed to inertial contributions leading to nutation of the magnetization vector around its angular momentum. Hence, an optical and non-resonant excitation of inertial magnetization dynamics can trigger and control different magnetic processes, ranging from demagnetization via nutation to precession in a single device. These findings will have profound implications for the understanding of ultrafast spin dynamics and magnetization switching.

The dynamics of magnetization in a magnetically ordered material is governed by precession [1]. Macroscopically, this precession leads to magnetic resonance phenomena that are used in a wide range of applications, from materials characterization to medical diagnostics. Microscopically, spin precession, or more precisely the precession of the spin's magnetic moment, explains the existence of spin waves and – in its quantized form – magnons as quasiparticles for the excitation of a magnetic ground state. Magnons are in the focus of contemporary spintronics [2, 3] with applications in sensor devices, data processing and energy efficient computing [4]. However, since spins are quantized angular momenta, there must be analogies to the mechanics of rotating bodies. If the rotation axis of a mechanical gyroscope is tilted away from the direction of the gravitational field by means of an external force, it will start to precess around the gravitational field, maintaining a constant angle with it. But there is a second type of dynamics: if one disturbs the precession such that the rotation axes of the gyroscope and its angular momentum are no longer aligned, an additional motion of the gyroscope around the angular momentum axis appears, known as the nutation [5, 6].

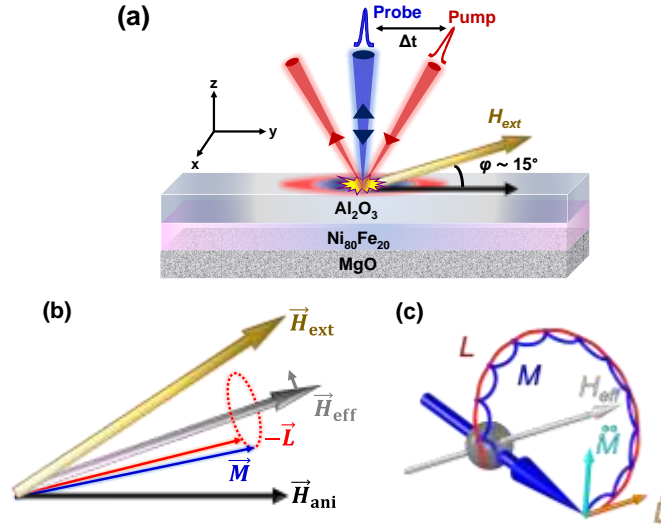


FIG. 1. (a) Schematic of the pump-probe experiment. (b) The pump pulse leads to a sudden reduction of the magnetization \vec{M} which, in turn, leads to a sudden tilting of the effective field \vec{H}_{eff} so that the equilibrium direction for the magnetization vector changes within some hundred fs. Consequently, the angular momentum \vec{L} starts to precess. (c) Magnetic inertia causes the dynamics of the magnetization to be separated from the angular momentum dynamics. As the angular momentum starts to precess around the effective field, the magnetization accelerates toward the effective field direction, initiating nutation dynamics on top of precession.

In analogy to the magnetization dynamics, the axis of rotation of the gyroscope defines the magnetization. In principle, the orientation of the magnetization can deviate from the associated total angular momentum [7-11] (and in the following, we will not distinguish spin and orbital contributions to the total angular momentum of the electronic system). For a gyroscope, the nutation dynamics can be triggered by a sudden torque pulse. In this work, we demonstrate that – in complete analogy to the mechanical case – we can trigger magnetic nutation via a sudden excitation of the magnetic system of a thin $\text{Ni}_{80}\text{Fe}_{20}$ (Permalloy or Py) film with an ultrashort laser pulse (Fig 1a). This ultrashort pulse leads to an abrupt tilting of the effective field acting on the spins' magnetic moments, which initiates a precession of the angular momentum (Fig. 1(b)). Crucially, the magnetic inertia leads to a separation of the dynamics of the magnetization from that of the angular momentum of the spin system, initiating nutation. This effect is sketched in Fig. 1(c): In the absence of inertia these dynamics would set in instantaneously with an abrupt change of the magnetic velocity, and magnetization and angular momentum would always be parallel. Considering inertia, the kinetic energy cannot increase instantaneously. Instead, as we will show later on, the magnetization starts to accelerate towards the effective field direction giving rise to nutation. The additional nutation is clearly a consequence of the sudden change of the effective field direction.

According to theoretical predictions [7-19] nutation could add a rich variety of effects to the magnetization dynamics, including new nutational resonances [8, 19], nutational spin waves [20-22], a shift of the known precessional resonances [19, 23], and even switching processes driven via a resonant excitation of nutation [24, 25] appears to be possible. However, all these studies are purely theoretical and – despite its fundamental importance – the experimental investigation of nutation effects is still in its infancy. Only recently, the resonant excitation of inertial spin dynamics has been experimentally observed, where THz pump-optical probe measurements were used to trigger and detect the nutation resonance [26, 27]. However, our results go beyond the mere demonstration of the existence of magnetic nutation, as previously shown in [26, 27], but show that the separation of the angular momentum from its magnetic moment is an inherent phenomenon occurring during the relaxation of a non-equilibrium excitation of a magnetic system using ultrashort optical pulses. Moreover, we provide a detailed theoretical understanding of the observed nutation dynamics. Thus, our study allows us to control the integration of different processes of magnetization dynamics, ranging from ultrafast demagnetization via nutation to precession in a single experiment.

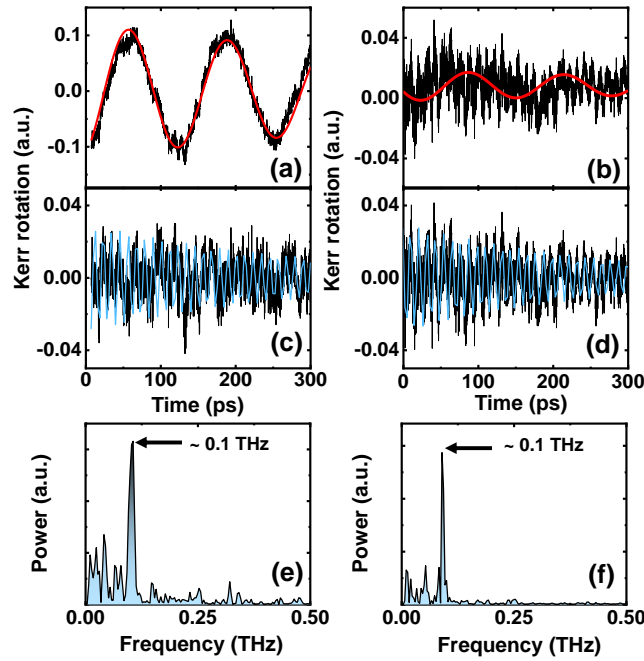


FIG. 2. Time-resolved Kerr rotation data measured up to 300 ps for (a) 5 nm and (b) 2.8 nm Py sample measured at $\mu_0 H_{\text{ext}} = 113$ mT and $F = 4.6 \text{ mJ cm}^{-2}$ are shown. Black lines are the experimental data and the red lines represents the FMR background. The background subtracted data for (c) 5 nm and (d) 2.8 nm Py sample. The blue lines correspond to the damped sinusoidal fit to the data points. The corresponding FFT power spectra of (e) 5 nm and (f) 2.8 nm Py sample showing a strong peak at ~ 0.1 THz.

Spin dynamics triggered by sudden excitation of a thin $\text{Ni}_{80}\text{Fe}_{20}$ film (thickness of 5 nm and 2.8 nm) with an ultrashort optical pulse was observed using a time-resolved magneto-optical Kerr effect (TR-MOKE) setup based on a two-color, non-collinear pump-probe technique (Fig 1(a) and section S1 of the Supplemental Materials [28]). The samples are fabricated on double-sided polished MgO substrates by molecular beam epitaxy (MBE) technique at room temperature and are capped with 3 nm Al_2O_3 layer. After the femtosecond (fs) pump pulse, the magnetization of the system is partially or completely lost within hundreds of fs, which is known as ultrafast demagnetization [29-31]. This is generally followed by a fast recovery of magnetization within sub-ps to a few ps and a slower recovery within hundreds of ps, known as fast and slow remagnetization. The slower recovery is accompanied by a precession of the magnetization [31-34]. On the shorter time scales of this slow recovery period (< 300 ps), we have observed that the usual precessional dynamics is enriched by an additional oscillation with larger frequency. To quantify the frequencies

of these oscillations, we have recorded time-resolved MOKE data up to 300 ps with very high time step resolution and subtracted the Ferromagnetic resonance (FMR) background. The time-resolved Kerr signal for 5 nm and 2.8 nm Py samples along with the corresponding FFT power spectra, showing a clear mode at ~ 0.1 THz in both cases, are plotted in Fig. 2(c) / (d) and 2(e) / (f), respectively. Next, we scanned the time-resolved traces (with an interval of 100 ps), and performed the FFT in each successive time window. The resulting frequency vs. time profiles for the two samples (5 nm and 2.8 nm Py) measured at different magnetic fields and pump fluences are summarized in Fig. 3. In all cases, a distinct mode is observed at ~ 0.1 THz, which we assign to the nutation. The nutation frequency shows a negligible dependence on the applied magnetic field and pump fluence. The frequency vs. time plots obtained from the time-resolved summed signals are shown in the section S2 of the supplemental materials [28], where we do not see any mode at ~ 0.1 THz. This is a strong criterion for interpreting our 0.1 THz driven oscillation as purely magnetically driven. An alternative interpretation for such high-frequency dynamics could be exchange-dominated perpendicular standing spin-wave (PSSW) modes across the film thickness. However, we can exclude these modes to be relevant here, since theoretically predicted PSSW modes in Py films of similar thickness appear at much higher frequencies. The calculated PSSW mode frequencies are ~ 1 THz and ~ 0.5 THz for 2.8 nm and 5 nm thick Py films, respectively. Additionally, the PSSW modes exhibit an inverse relationship with sample thickness, which is not observed here.

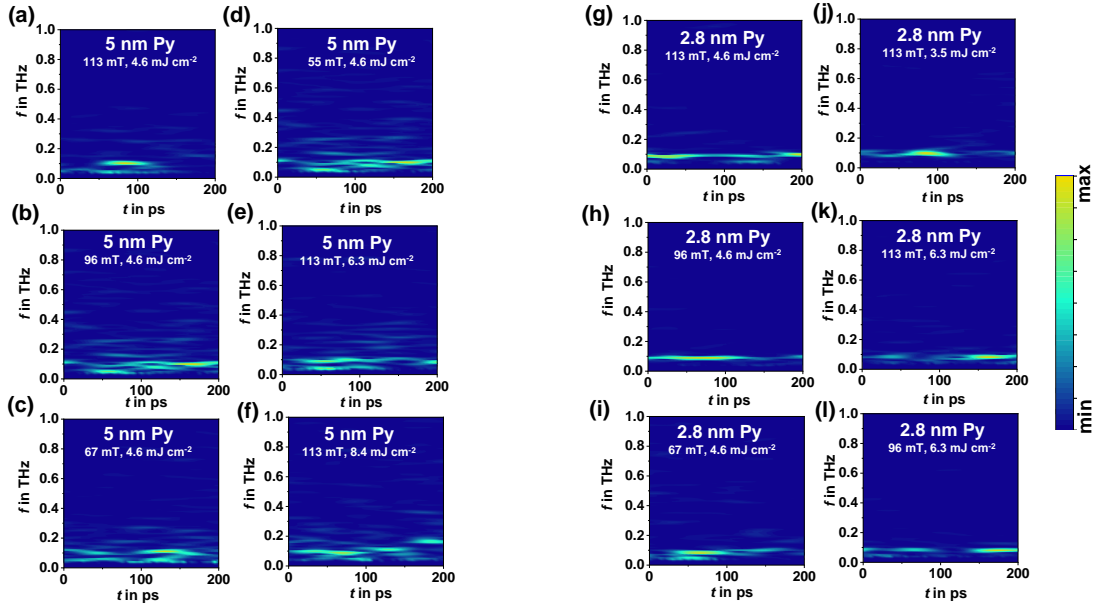


FIG. 3. Frequency vs. time plots obtained from the FFT of the background subtracted experimental time-resolved Kerr rotation signals for the 5 nm and 2.8 nm Py samples at different magnetic fields and pump fluences showing a clear mode at ~ 0.1 THz in each case. The sample thickness and values of $\mu_0 H_{\text{ext}}$, F are shown in the respective plots.

For nearly 90 years, magnetizations dynamics has been described by the Landau-Lifshitz [LL-equation], which – with minor modifications by Gilbert – is now known as Landau-Lifshitz-Gilbert (LLG) equation [1, 35],

$$\frac{d\vec{M}}{dt} = -\gamma \vec{M} \times \left[\mu_0 \vec{H}_{\text{eff}} - \frac{\alpha}{\gamma M_S} \frac{d\vec{M}}{dt} \right] \quad (1)$$

where γ is the gyromagnetic ratio, M_S the saturation magnetization, α the Gilbert damping constant, and \vec{H}_{eff} the effective field which includes contributions from an external magnetic field but also from exchange interactions or anisotropies. The first term on the right-hand side of equation (1) accounts for the precession of magnetization vector (\vec{M}) around \vec{H}_{eff} . The second term with a first-order time derivative of \vec{M} is the Gilbert damping term [34], which occurs due to the transfer of energy and angular momentum of \vec{M} to the environmental degrees of freedom and leads

to a relaxation of \vec{M} towards the direction of \vec{H}_{eff} . However, the dynamics of the angular momentum and the magnetization of a magnetic material are not necessarily aligned since the magnetization vector cannot instantaneously follow the angular momentum. This effect can be described by an additional second-order time derivative term in the equation of motion that plays the role of inertia for the magnetization. The resulting inertial Landau-Lifshitz-Gilbert (LLG) equation reads [8, 36],

$$\frac{d\vec{M}}{dt} = -\gamma\vec{M} \times \left[\mu_0\vec{H}_{\text{eff}} - \frac{\alpha}{\gamma M_S} \frac{d\vec{M}}{dt} - \frac{\eta}{\gamma M_S} \frac{d^2\vec{M}}{dt^2} \right] \quad (2)$$

The second order derivative term on the right-hand side of equation (2) gives rise to inertia and can lead to an additional oscillatory motion superimposed on top of the usual precession dynamics, known as nutation. The time scale of the nutation is defined by the parameter η which is expected to be in the range of picoseconds or even less, leading to oscillations of much higher frequency (in the sub-terahertz range) than those associated with spin precession (in the gigahertz range). Note, that the definition of η in equation (2) is slightly different to former work [8]. Here it is a time scale that is independent of the damping constant α . Different types of derivations of the inertial term include phenomenological arguments [9] as well first principles calculations [11] and a relativistic approach based on the Dirac equation [15, 18]. The determination of the value of the parameter η is, however, an open question, as different studies indicate values ranging from a few femtoseconds to hundreds of picoseconds [8, 10, 12, 26]. Assuming a certain value for the parameter η , however, the angular frequencies for precession and nutation in a magnetic field $\mu_0 H_{\text{ext}}$ can be approximated from the following formula [25, 36]:

$$\omega_{\text{nu}} = -\frac{\sqrt{1+4\gamma\eta\mu_0 H_{\text{ext}}} + 1}{2\eta} \approx -\frac{1}{\eta} \quad \omega_{\text{p}} = \frac{\sqrt{1+4\gamma\eta\mu_0 H_{\text{ext}}} - 1}{2\eta} \approx \gamma\mu_0 H_{\text{ext}} \quad (3)$$

Similar expressions, which reproduce the first term of the expansions, were also derived in Ref. [13]. Note the different sign of ω_{nu} and ω_{p} , which indicates that the sense of rotation of nutation is always opposite to that of precession. In our experiments, we observed a nutation frequency of ~ 0.1 THz, so that for our samples, $\eta = 1/\omega_{\text{nu}}$ comes out to be ~ 1.6 ps, which is about 5 times larger than the corresponding value reported in [26]. Further investigation of this time-dependent behavior will give more insight into the inertial dynamics.

For a deeper analysis of the dynamics of magnetization and angular momentum in the inertial regime we perform atomistic spin dynamics simulations based on the classical Heisenberg model and the LLG equation (details are provided in the section S3 of the supplemental materials [28]). To be able to compare with our experiments, we use a permalloy model from [37], where the atomic magnetic moments are located on an fcc lattice with 20% iron atoms and 80% nickel atoms. We use the nutation parameter of $\eta = 1.6$ ps obtained from our experiments above and a magnetic field $\vec{B} = (0, 110, 30)^T$ mT with an out-of-plane component as in the experiments. Then we solve the stochastic LLG equation on an atomistic level as described in the methods section and calculate the time-dependent magnetization curve $M_z(t)$ shown in Fig. 4(a). After a thermal excitation with a heat pulse the system shows the precessional dynamics around the effective field with a period in the range of hundred picoseconds. Due to the nutation a second oscillation on the single picosecond time scale arises. This can be seen in the inset of Fig. 4(a), showing that the nutational mode has a period in the range of some picoseconds. The Fourier transform in Fig. 4(b) shows, that the nutation frequency is ~ 0.1 THz. With these parameters, the nutation frequency is very similar to the experimentally determined one from Fig. 3 and also matches the analytical expectation from Eq. 3. Note, however, that here the actual frequency and not the angular frequency is considered.

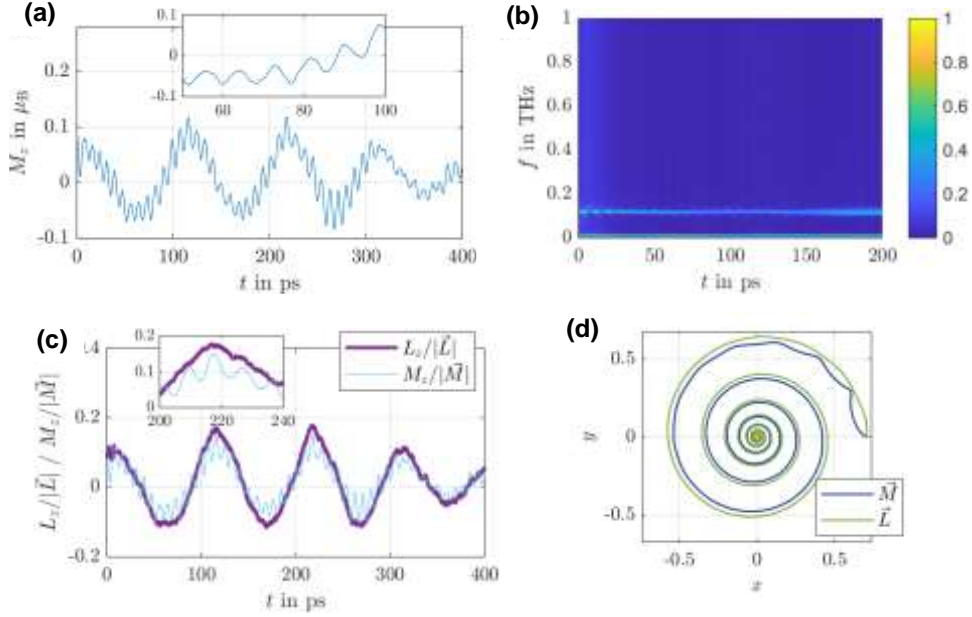


FIG. 4. (a) Time-dependent magnetization curve of the simulated permalloy model after an excitation with a rectangular ultrashort heat pulse. The magnetization shows both precession and nutation. (b) Frequency vs time plot of the spectral power density $P_z \cdot f^2$, unveiling the nutation frequency of ~ 0.1 THz and the precession frequency of ~ 0.01 THz. The spectral power density is multiplied with f^2 to reduce the thermal background noise. (c) Temporal dependence of the reduced magnetization and angular momentum of the out-of-plane component, showing that the magnetization nutates around the angular momentum. (d) Sketch of the trajectories of magnetization and angular momentum following a sudden tilting of the effective field, which is then perpendicular to the image plane.

Furthermore, our simulations allow us to investigate the behavior of the angular momentum \vec{L} of the system, which is – due to the inertia – no longer parallel to the magnetization [36]. The relation between the magnetization \vec{M} and the corresponding angular momentum \vec{L} (per volume) is given by [36],

$$\vec{L} = \frac{1}{\gamma} \vec{M} - \frac{\eta}{\gamma M_S} \vec{M} \times \frac{d}{dt} \vec{M} \quad (5)$$

The temporal behavior of the system's angular momentum is shown in Fig. 4(c). On long time scales the angular momentum and the magnetization show the same precessional dynamics in the frequency range of single GHz, which is identical to the case of vanishing nutation. We point out that the nutation mode is only reflected in the magnetization, since only the magnetic moments nutate around their associated angular momentum. On the contrary, the angular momentum just precesses around the external field. As our simulations demonstrate, the nutation leads to a separation of the magnetic moment from its angular momentum, not only on the atomistic scale but also on a macroscopic level, splitting up \vec{L} and \vec{M} for a system of interacting magnetic moments. The sudden emergence of the nutation, as triggered by the laser pulse, can be understood when bringing the ILLG into an explicit form [36] that resemble Newton's equation of motion:

$$\eta \frac{\partial^2}{\partial t^2} \vec{M} = -\frac{\gamma}{M_S} \vec{M} \times (\vec{M} \times \mu_0 \vec{H}_{\text{eff}}) - \alpha \frac{\partial}{\partial t} \vec{M} - \frac{1}{M_S} \vec{M} \times \frac{\partial}{\partial t} \vec{M} - \eta \frac{1}{M_S^2} \vec{M} \left(\frac{\partial}{\partial t} \vec{M} \right)^2 \quad (6)$$

A sudden tilting of the effective field away from the magnetization direction starts the dynamics. For an initially resting magnetization \vec{M} only the first term in Eq. 6 is non-zero and accelerates the magnetization towards the effective field, perpendicular to the precession direction. After this initial acceleration the other terms have to be considered, leading to the magnetization dynamics as sketched schematically in Fig. 4(d). For the angular momentum, however, the initial

acceleration of \vec{M} leads to an immediate velocity $-\frac{\eta}{\gamma M_S} \vec{M} \times \frac{d^2}{dt^2} \vec{M} = -\vec{M} \times \mu_0 \vec{H}_{\text{eff}}$ according to Eq. 5 and Eq. 6, pointing in precession direction. So, while the magnetization is indeed inertial and accelerates due to the nutation term in the ILLG, the velocity of the angular momentum increases discontinuously, which makes the angular momentum inertial-free in contrast to the magnetization. An important indicator of the dynamics of nutation is that it decays more rapidly than precession.

In conclusion, using the TR-MOKE technique and atomistic spin dynamics simulations, we show that in thin $\text{Ni}_{80}\text{Fe}_{20}$ films coherent magnetic nutation can arise from a strong non-equilibrium of the spin system after optical excitation separating the dynamics of the magnetic moment from those of its angular momentum. These findings cannot be explained by the ubiquitous Landau-Lifshitz-Gilbert equation but agree with an extension of this equation of motion that contains a second-order time derivative describing inertia. The magnetic nutation is in the high-frequency regime (close to THz range) and superimposed on the precession dynamics (GHz range). Our results demonstrate that the coherent magnetic nutation and the corresponding separation of the angular momentum from its magnetic moment is an intrinsic phenomenon occurring during the relaxation of an ultrafast non-equilibrium excitation of a magnet and does not only rely on a resonant excitation of the spin system [26, 27]. Hence, an optical excitation of inertial spin dynamics can enable and control the integration of different magnetic processes, ranging from demagnetization via nutation to precession in one device. This will have significant consequences in the field of spintronics. The discovery of Einstein and de Haas [38] has connected magnetic moment with angular momentum, and, hence, linked electro-dynamics with mechanics. Our findings show that nutation can separate effects that rely on magnetization dynamics from those that rest on properties of the associated angular momentum. While most effects in spintronics rely on magnetic or magneto-optic effects, the recently discovered ultrafast transfer of spin angular momentum into the lattice [39] rests on (spin plus mechanical) angular momentum conservation. Similarly, the recently established research into chiral phonons [40, 41] can connect mechanical with magnetic degrees of freedom [42,43]. The separation of these quantities – magnetic moment and angular momentum – on ultrashort time scales will have profound implications for the understanding of ultrafast spin related physics.

Funding for this work was provided by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) under Grant No. TRR 173-268565370, Spin+X (Projects No. B11 and B03), Grant No. 318592081, and Grant No. 425217212-SFB 1432.

1. L. Landau and E. Lifshitz, On the Theory of the dispersion of magnetic permeability in ferromagnetic bodies. *Phys. Z. Sowjetunion* **8**, 153 (1935).
2. A. V. Chumak, V. I. Vasyuchka, A. A. Serga, and B. Hillebrands, Magnon spintronics. *Nat. Phys.* **11**, 453 (2015).
3. P. Pirro, A. Vasyuchka, A. A. Serga, and B. Hillebrands, Advances in coherent magnonics. *Nat. Rev. Mater.* **6**, 1114 (2021).
4. T. Dietl, D. D. Awschalom, M. Kaminska, and H. Ohno, Spintronics, Hardback ISBN: 9780080449562, Elsevier (2008).
5. H. Goldstein, Classical Mechanics, Addison-Wesley, Reading, MA (1980).
6. R. Feynman, R. Leighton, and M. Sands, The Feynman Lectures on Physics (CIT, 1963), Vol. I, 20.6–7 for the description of the gyroscope and Vol. II 34–2 to 34–5 for the magnetic precession.
7. M. Fahnle, D. Steiauf, and C. Illg, Generalized Gilbert equation including inertial damping: Derivation from an extended breathing Fermi surface model. *Phys. Rev. B* **84**, 172403 (2011).
8. M.-C. Ciornei, J. M. Rubí, and J.-E. Wegrowe, Magnetization dynamics in the inertial regime: Nutation predicted at short time scales. *Phys. Rev. B* **83**, 020410(R) (2011).
9. J.-E. Wegrowe, M.-C. Ciornei, Magnetization dynamics, gyromagnetic relation, and inertial effects. *Am. J. Phys.* **80**, 607 (2012).
10. E. Olive, Y. Lansac, and J.-E. Wegrowe, Beyond ferromagnetic resonance: The inertial regime of the magnetization dynamics, *Appl. Phys. Lett.* **100**, 192407 (2012).
11. S. Bhattacharjee, L. Nordstrom, and J. Fransson, Atomistic spin dynamic method with both damping and moment of inertia effects included from first principles. *Phys. Rev. Lett.* **108**, 057204 (2012).
12. D. Böttcher, and J. Henk, Significance of nutation in magnetization dynamics of nanostructures. *Phys. Rev. B* **86**, 020404(R) (2012).
13. E. Olive, Y. Lansac, M. Meyer, M. Hayoun, and J.-E. Wegrowe, Deviation from the Landau-Lifshitz-Gilbert equation in the inertial regime of the magnetization. *J. Appl. Phys.* **117**, 213904 (2015).
14. T. Kikuchi, and G. Tatara, Spin dynamics with inertia in metallic ferromagnets. *Phys. Rev. B* **92**, 184410 (2015).
15. R. Mondal, M. Berritta, A. K. Nandy, and P. M. Oppeneer, Relativistic theory of magnetic inertia in ultrafast spin dynamics. *Phys. Rev. B* **96**, 024425 (2017).
16. S. Giordano, and P.-M. Déjardin, Derivation of magnetic inertial effects from the classical mechanics of a circular current loop. *Phys. Rev. B* **102**, 214406 (2020).
17. I. Makhfudz, E. Olive, and S. Nicolis, Nutation wave as a platform for ultrafast spin dynamics in ferromagnets. *Appl. Phys. Lett.* **117**, 132403 (2020).
18. R. Mondal, M. Berritta, and P. M. Oppeneer, Generalisation of Gilbert damping and magnetic inertia parameter as a series of higher-order relativistic terms. *J. Phys. Cond. Matter: an Institute of Physics journal* **30**, 265801 (2018).

19. R. Mondal, S. Großenbach, L. Rózsa, and U. Nowak, Nutation in antiferromagnetic resonance. *Phys. Rev. B* **103**, 104404 (2021).
20. M. Cherkasskii, M. Farle, and A. Semisalova, Dispersion relation of nutation surface spin waves in ferromagnets. *Phys. Rev. B* **103**, 174435 (2021).
21. S. V. Titov, W. J. Dowling, Y. P. Kalmykov, and M. Cherkasskii, Nutation spin waves in ferromagnets. *Phys. Rev. B* **105**, 214414 (2022).
22. R. Mondal, and L. Rózsa, Inertial spin waves in ferromagnets and antiferromagnets. *Phys. Rev. B* **106**, 134422 (2022).
23. M. Cherkasskii, I. Barsukov, R. Mondal, M. Farle, and A. Semisalova, Theory of inertial spin dynamics in anisotropic ferromagnets. *Phys. Rev. B* **106**, 054428 (2022).
24. K. Neeraj, M. Pancaldi, V. Scalera, S. Perna, M. d'Aquino, C. Serpico, and S. Bonetti, Magnetization switching in the inertial regime. *Phys. Rev. B* **105**, 054415 (2022).
25. L. Winter, S. Großenbach, U. Nowak, and L. Rózsa, Nutational switching in ferromagnets and antiferromagnets. *Phys. Rev. B* **106**, 214403 (2022).
26. K. Neeraj, N. Awari, S. Kovalev, D. Polley, N. Z. Hagström, S. S. P. K. Arekapudi, A. Semisalova, K. Lenz, B. Green, J.-C. Deinert, I. Ilyakov, M. Chen, M. Bawatna, V. Scalera, M. d'Aquino, C. Serpico, O. Hellwig, J.-E. Wegrowe, M. Gensch, and S. Bonetti, Inertial spin dynamics in ferromagnets. *Nat. Phys.* **17**, 245 (2021).
27. V. Unikandanunni, R. Medapalli, M. Asa, E. Albisetti, D. Petti, R. Bertacco, E. E. Fullerton, and S. Bonetti, Inertial Spin Dynamics in Epitaxial Cobalt Films. *Phys. Rev. Lett.* **129**, 237201 (2022).
28. Supplemental Materials [URL to be provided by the publisher] containing S1. Time-resolved MOKE experiments, S2. Time-resolved Sum signals, S3. Atomistic Spin Dynamics simulations.
29. E. Beaurepaire, J.-C. Merle, A. Daunois, and J.-Y. Bigot, Ultrafast Spin Dynamics in Ferromagnetic Nickel. *Phys. Rev. Lett.* **76**, 4250 (1996).
30. J.-Y. Bigot, M. Vomir, and E. Beaurepaire, Coherent ultrafast magnetism induced by femtosecond laser pulses. *Nat. Phys.* **5**, 515, (2009).
31. A. De, A. Lentfert, L. Scheuer, B. Stadtmüller, G. von Freymann, M. Aeschlimann, and P. Pirro, Coherent and incoherent magnons induced by strong ultrafast demagnetization in thin permalloy films. *Phys. Rev. B* **109**, 024422 (2024).
32. M. van Kampen, C. Jozsa, J. T. Kohlhepp, P. LeClair, L. Lagae, W. J. M. de Jonge, and B. Koopmans, All-optical probe of coherent spin waves, *Phys. Rev. Lett.* **88**, 227201 (2002).
33. B. Koopmans, J. J. M. Ruigrok, F. Dalla Longa, W. J. M. de Jonge, Unifying Ultrafast Magnetization Dynamics. *Phys. Rev. Lett.* **95**, 267207 (2005).
34. M. Vomir, L. H. F. Andrade, L. Guidoni, E. Beaurepaire, and J.-Y. Bigot, Real Space Trajectory of the Ultrafast Magnetization Dynamics in Ferromagnetic Metals. *Phys. Rev. Lett.* **94**, 237601 (2005).
35. T. Gilbert, A phenomenological theory of damping in ferromagnetic materials, *IEEE Trans. Magn.* **40**, 3443 (2004).

36. R. Mondal, L. Rózsa, M. Farle, P. M. Oppeneer, U. Nowak, and M. Cherkasskii, Inertial effects in ultrafast spin dynamics. *J. Mag. Mag. Mat.* **579**, 170830 (2023).
37. D. Hinzke, U. Atxitia, K. Carva, P. Nieves, O. Chubykalo-Fesenko, P. M. Oppeneer, and U. Nowak, Multiscale modeling of ultrafast element-specific magnetization dynamics of ferromagnetic alloys. *Phys. Rev. B* **92**, 054412 (2015).
38. A. Einstein, and W. J. de Haas, Experimental proof of the existence of Ampère's molecular currents. *KNAW Proceedings* **18 I**, 696 (1915).
39. S. R. Tauchert, M. Volkov, D. Ehberger, D. Kazenwadel, M. Evers, H. Lange, A. Donges, A. Book, W. Kreuzpaintner, U. Nowak, and P. Baum, Polarized phonons carry angular momentum in ultrafast demagnetization. *Nature* **602**, 73 (2022).
40. L. Zhang, Q. Niu, Chiral Phonons at High-Symmetry Points in Monolayer Hexagonal Lattices. *Phys. Rev. Lett.* **115**, 115502 (2015).
41. H. Zhu, J. Yi, M. Li, J. Xiao, L. Zhang, C. Yang, R. Kaindl, L. Li, Y. Wang, and X. Zhang, Observation of chiral phonons. *Science* **359**, 579 (2018).
42. J. Cui, E.V. Boström, M. Ozerov, F. Wu, Q. Jiang, J. H. Chu, C. Li, F. Liu, X. Xu, A. Rubio, and Q. Zhang, Chirality selective magnon-phonon hybridization and magnon-induced chiral phonons in a layered zigzag antiferromagnet. *Nat. Commun.* **14**, 3396 (2023).
43. K. Kim, E. Vetter, L. Yan, C. Yang, Z. Wang, R. Sun, Y. Yang, A. H. Comstock, X. Li, J. Zhou, L. Zhang, W. You, D. Sun, and J. Liu, Chiral-phonon-activated spin Seebeck effect. *Nat. Mater.* **22**, 322 (2023).

Supplemental Materials

S1. Time-resolved MOKE experiments

The experimental setup is shown schematically in Fig. 1(a) of the main article. Spin dynamics are measured by a TR-MOKE setup based on a two-color, non-collinear, all-optical pump-probe technique. An amplified 1 kHz Ti:sapphire laser system (Astrella, Coherent; $\lambda = 800$ nm, repetition rate ~ 1 kHz, and pulse width of ~ 35 fs) forms the experimental base, which is used to pump the spin dynamics. The second harmonic ($\lambda = 400$ nm) of the amplifier pulses is sent through a mechanical delay line and used to probe of the dynamics. The probe is normally incident on the sample, while the pump is incident at an angle ($\sim 30^\circ$ with respect to the surface normal). An external magnetic field (H_{ext}) is tilted at a small angle ($\varphi \sim 15^\circ$) to the plane of the sample. This provides a finite out-of-plane demagnetization field, which is transiently modified by the pump pulse to induce both precession and nutation of the spins. For a completely in-plane configuration of the external (and thus effective) magnetic field, no optically induced precession (and nutation) is observed. To exclude any non-magnetic signal, we perform the measurements for two opposite directions of the sample magnetization and extract the pure magnetic response from the difference of the two resulting Kerr signals. All experiments are carried out at room temperature and under ambient conditions.

S2. Time-resolved sum signals

The frequency vs. time plots obtained from the time-resolved sum signals. The sum signal is generally dominated by purely optically induced transient artifacts and shows no mode at ~ 0.1 THz for either Py sample. Thus, this is a strong criterion for interpreting our 0.1 THz driven oscillation as purely magnetically driven.

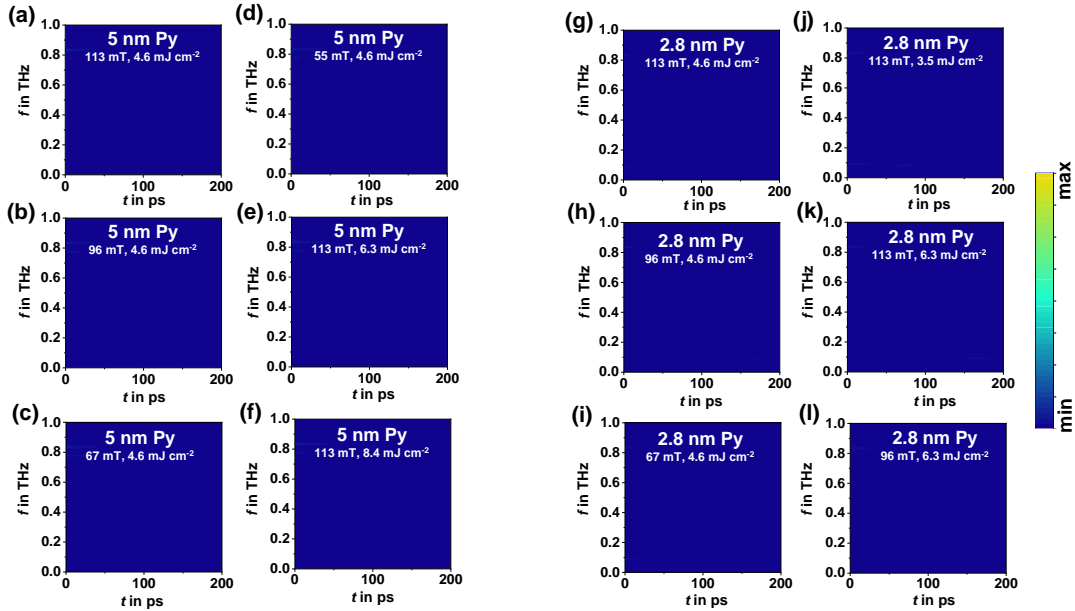


FIG. S1. Frequency vs. time plots obtained from the FFT of the time-resolved sum signals for the 5 nm and 2.8 nm Py samples at different values of magnetic field and pump fluences. The sample thickness and the values of $\mu_0 H_{\text{ext}}$ and F are shown in the respective plots. We do not observe any mode at ~ 0.1 THz in the non-magnetic sum signals.

S3. Atomistic spin dynamics simulations

Permalloy is modeled as a doped fcc-lattice crystal consisting of 20% iron and 80% nickel atoms. We use a Heisenberg model to describe the interactions and energy contributions of the magnetic system. The magnetic moments are treated as classical, three-dimensional vectors $\vec{\mu}_i$ with a length of $2.637 \mu_B$ for iron and $0.628 \mu_B$ for nickel. i indexes the

lattice site, where μ_B is the Bohr magneton. In the following we will consider normalized and dimensionless magnetic moments $\vec{e}_i = \frac{\vec{\mu}_i}{\mu_i}$ with their corresponding magnitude μ_i . Our Hamiltonian then reads

$$H\{\vec{e}_i\} = - \sum_{i,j} J_{ij} \vec{e}_i \cdot \vec{e}_j - d_z \sum_i (e_i^z)^2 - \vec{B} \sum_i \mu_i \vec{e}_i,$$

comprising an isotropic Heisenberg exchange, second order on-site anisotropy and the Zeeman term. The exchange parameters are taken from [37], considering the exchange up to a distance of 1.704 nm. To model the shape anisotropy d_z is set to -0.1 meV, leading to a hard z-axis. The Zeeman term describes the coupling to the external field $\vec{B} = (0, 110, 30)^T$ mT.

To describe the dynamics, the explicit form of the inertial Landau-Lifshitz-Gilbert equation is used, which reads

$$\frac{\partial^2}{\partial t^2} \vec{e}_i = - \frac{\gamma}{\eta \mu_i} \vec{e}_i \times (\vec{e}_i \times \vec{H}_i) - \frac{\alpha}{\eta} \frac{\partial}{\partial t} \vec{e}_i - \frac{1}{\eta} \vec{e}_i \times \frac{\partial}{\partial t} \vec{e}_i - \vec{e}_i \left(\frac{\partial}{\partial t} \vec{e}_i \right)^2$$

and is equivalent to equation (2). The effective field

$$\vec{H}_i = - \frac{\partial H}{\partial \vec{e}_i} + \vec{\xi}_i,$$

describes the effect of the Hamiltonian on the dynamics of the magnetic moments. $\vec{\xi}_i$ is a Gaussian white noise with

$$\langle \vec{\xi}_i(t) \rangle = 0, \quad \langle \xi_{iv}(t) \xi_{j\eta}(t') \rangle = \frac{2\mu_i \alpha k_B T}{\gamma_i} \delta_{ij} \delta_{v\eta} \delta(t - t'),$$

taking into account the coupling to a heat bath with temperature T . i and j are lattice site indices, v and η represent the Cartesian directions. Due to the delta-functions on the right the noise is uncorrelated in both, space and time. On this basis the temporal evolution of a system of $N = 64^3$ spins with periodic boundary conditions is numerically computed via the stochastic Heun method. In addition, the angular momentum \vec{L}_i for each atomic magnetic moment is calculated by means of [36]

$$\vec{L}_i = \frac{\mu_i}{\gamma} \vec{e}_i - \frac{\eta \mu_i}{\gamma} \vec{e}_i \times \frac{\partial}{\partial t} \vec{e}_i$$

The gyromagnetic ratio is set to the one of a free electron $\gamma = 1.76 \cdot 10^{11} \frac{1}{\text{Ts}}$, the damping constant is set to $\alpha = 0.02$ and the temperature after the excitation to $k_B T = 25$ meV. The excitation is modelled by means of a rectangular heat pulse in the beginning of the simulation with a width of 8 ps and a height of $k_B T = 400$ meV. Note, that the length of the heat pulse in our simulations has to be much larger than that of the laser pulse. Due to the inertia, the spin system reacts slower, so that even the demagnetization takes more time. This is a strong indication that the LLG equation alone cannot describe the initial demagnetization phase completely but additional electronic processes also contribute to the demagnetization on femtosecond time scales.

The main output of the simulation is the system's magnetization

$$\vec{M}(t) = \frac{1}{N} \sum_i \frac{\mu_i}{\mu_B} \vec{e}_i(t),$$

which is here the averaged magnetic moment per lattice site and dimensionless. The system's angular momentum is given by

$$\vec{L}(t) = \frac{1}{N} \sum_i \vec{L}_i(t).$$

The spectral power density of the magnetization in the Fourier domain is computed via

$$P_\beta(f) = \left\langle \frac{|M_\beta^T(f)|^2}{T} \right\rangle$$

with the truncated Fourier transform

$$m_\beta^T(f) = \int_0^T (M_\beta(t) - \langle M_\beta \rangle) e^{-i2\pi f t} dt$$

and with $\beta \in \{x, y, z\}$.